

High gradient column dividing resistors

R. Damm

August 1965

Collider Accelerator Department
Brookhaven National Laboratory

U.S. Department of Energy

USDOE Office of Science (SC)

Notice: This technical note has been authored by employees of Brookhaven Science Associates, LLC under Contract No.AT-30-2-GEN-16 with the U.S. Department of Energy. The publisher by accepting the technical note for publication acknowledges that the United States Government retains a non-exclusive, paid-up, irrevocable, world-wide license to publish or reproduce the published form of this technical note, or allow others to do so, for United States Government purposes.

DISCLAIMER

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, nor any of their contractors, subcontractors, or their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or any third party's use or the results of such use of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof or its contractors or subcontractors. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

Accelerator Department
BROOKHAVEN NATIONAL LABORATORY
Associated Universities, Inc.
Upton, L.I. N.Y.

AGS DIVISION TECHNICAL NOTE

No. 4

R. Damm

August 24, 1965

During the testing of the resistors for the new short column, one of the test resistors failed at 114,000 volts. The present column design calls for a 15-section column with resistors running at 50,000 volts. The column may be shortened at some later date to a 10-section column with resistors running at 75,000 volts. It was the general feeling at the time of the failure that the resistors should not at any time be the limiting factor on the column design. Since the properties of the resin and the effect of high voltage on the resin over long periods of time are not known, a program was started to improve the overall properties of the resistor assemblies. The general idea is to improve the thermal conductivity of resin without any loss of electrical properties. The first test indicated a few things of interest.

1. Small amounts of filler will settle out of the casting unless a fast cure cycle is used.
2. Small amounts of filler have little effect on the properties of the casting.
3. The fillers used do not seem to lower the dielectric strength of the resin.

The second test in which a thermistor was bonded to the resistors indicated the following:

1. The temperature rise in Block 1 was about half that in Block 4.
2. Block 1 and Block 2 show a small difference even though there is twice as much filler in Block 1 as in Block 2. (Filler-boron-nitride).
3. Block 3 filled with alumina with the same ratio as Block 1 has a temperature rise about one third greater than Block 1.

The author feels that the resin system in Block 2 being lower in viscosity using only one half as much filler is the system to use in the casting of the final resistors.

Distribution: A. van Steenberg
T. Sluyters
A. Soukas
W. Schneider
R. Larson
T. Fishman
R. Zider

TABLE I

- Block # 1. 11 GRAMS BORON NITRIDE
205 GRAMS RESIN
- # 2 5 1/2 GRAMS BORON NITRIDE
202 GRAMS RESIN
- # 3 104 GRAMS ALUMINA
203 GRAMS RESIN
- # 4 52 GRAMS ALUMINA
201 GRAMS RESIN
- # 5 53 GRAMS SILICA FLOUR
201 GRAMS RESIN
- # 6 26.5 GRAMS SILICA FLOUR
202 GRAMS RESIN
- # 7 200 GRAMS RESIN
NO FILLER.

RESIN-RATIO 50 GRAMS SHELL EPON 815
50 GRAMS " " " 815
20 GRAMS " " " 815

SPECIAL BLOCK # 8

RESIN RATIO

200 GRAMS 815 (SHELL EPON)
40 GRAMS Z
98 GRAMS BORON NITRIDE

... 24 HOURS - No Post-Cure

TABLE II

CASTINGS WITH THERMISTORS BONDED TO RESISTORS.

Block # 1.

100 GRAMS	SHELL	EPON	815	
20 "	"	"	"	Z
50 "	BORON NITRIDE (325 MESH)			

Block # 2

100 GRAMS	SHELL	EPON	815	
20 GRAMS	"	"	"	Z
25 "	BORON NITRIDE			

Block # 3

100 GRAMS	SHELL	EPON	815	
20 "	"	"	"	Z
50 "	ALUMINA			


Block # 4

50 GRAMS	SHELL	EPON	815	
50 "	"	"	"	871
20 "	"	"	"	Z

PREHEAT RESINS BEFORE MIXING

CURE AT 140° F FOR 24 HOURS.
NO POST-CURE

FIGURE I

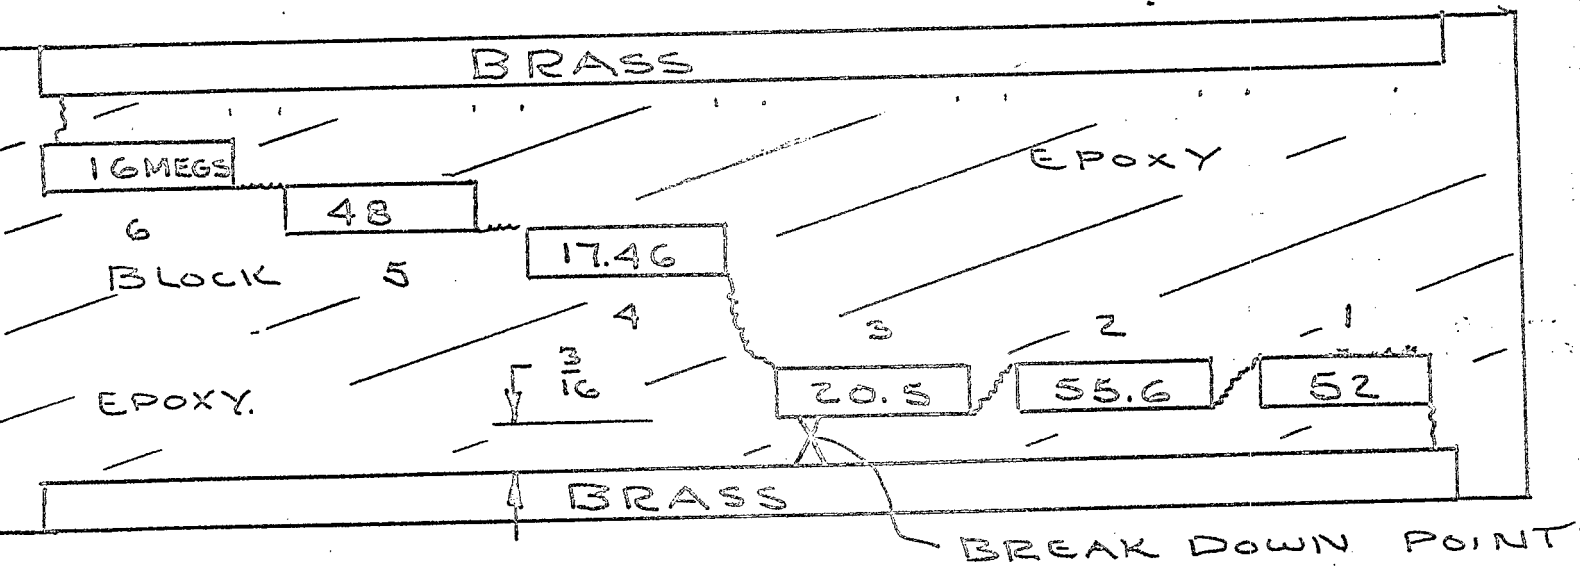


RESISTANCES GIVEN IN MEG-OHMS

POTTING RESIN RATIO	50 GRAMS	SHELL	EPON	815
	50	"	"	871
	20	"	"	2


BREAK DOWN AT ABOUT 114,000 VOLTS D.C.
IN A SF₆ BAG.

RESISTANCE MEASURED AFTER BLOCKS
WERE CUT APART.

RESISTANCE OF BLOCKS BEFORE CASTING
60 MEGS ± 10%.

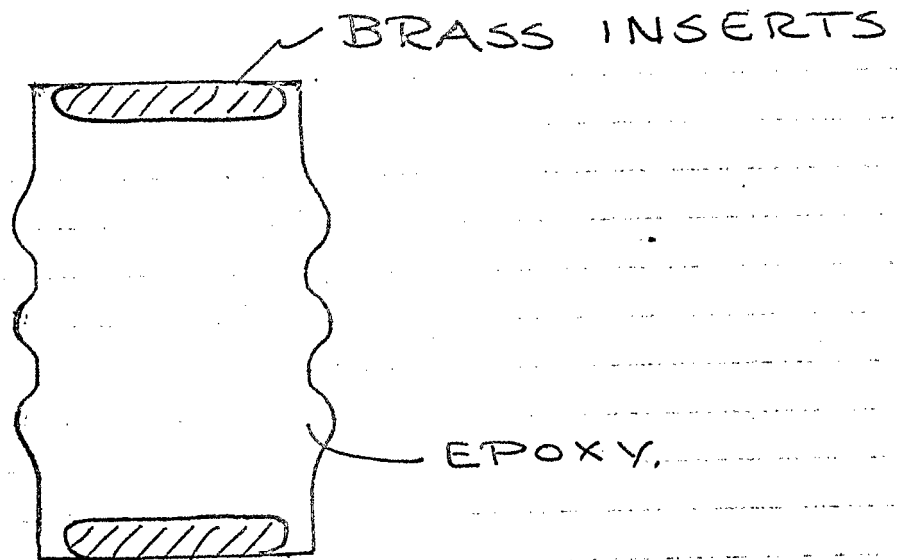

CROSS SECTION OF RESISTOR (FULL SCALE)

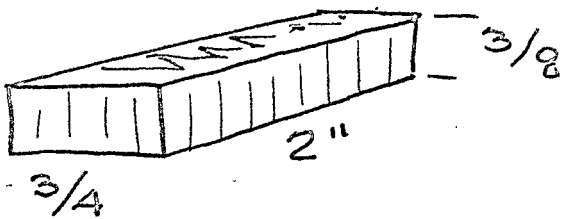

RESISTOR BLOCK 60 MEGS.

160 - 1.5 MEG - CARBON RESISTORS

PRINTED CIRCUIT FORMS CONNECTIONS

6 RESISTOR BLOCKS IN SERIES IN

FINISHED RESISTOR - 360 MEGS.

TEST VOLTAGE IN K.V.

24 21 18 15 12 9 4


TEST II
CURVE II

BLOCK NO.	FILLER % BY WT.
1	29.4% BORON NITRIDE
2	17.2% " "
3	29.4% ALUMINA
4	

TEMPERATURE C°

10 X 10 TO 1/2 INCH 47 1323
10 X 15 INCHES
REUFEL & ESSER CO.

TEMPERATURE RISE ΔT C°

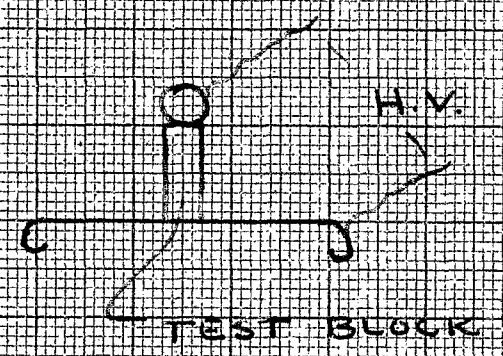


THERMISTOR
CALIBRATION CURVES

TEST
CURVES


BLOCK NO.

6. 5.6 5.2 4.8 4.4 4 3.6 3.2 2.8 2.4 2 1.6 1.2 .8 .4 0


DISTANCE IN INCHES

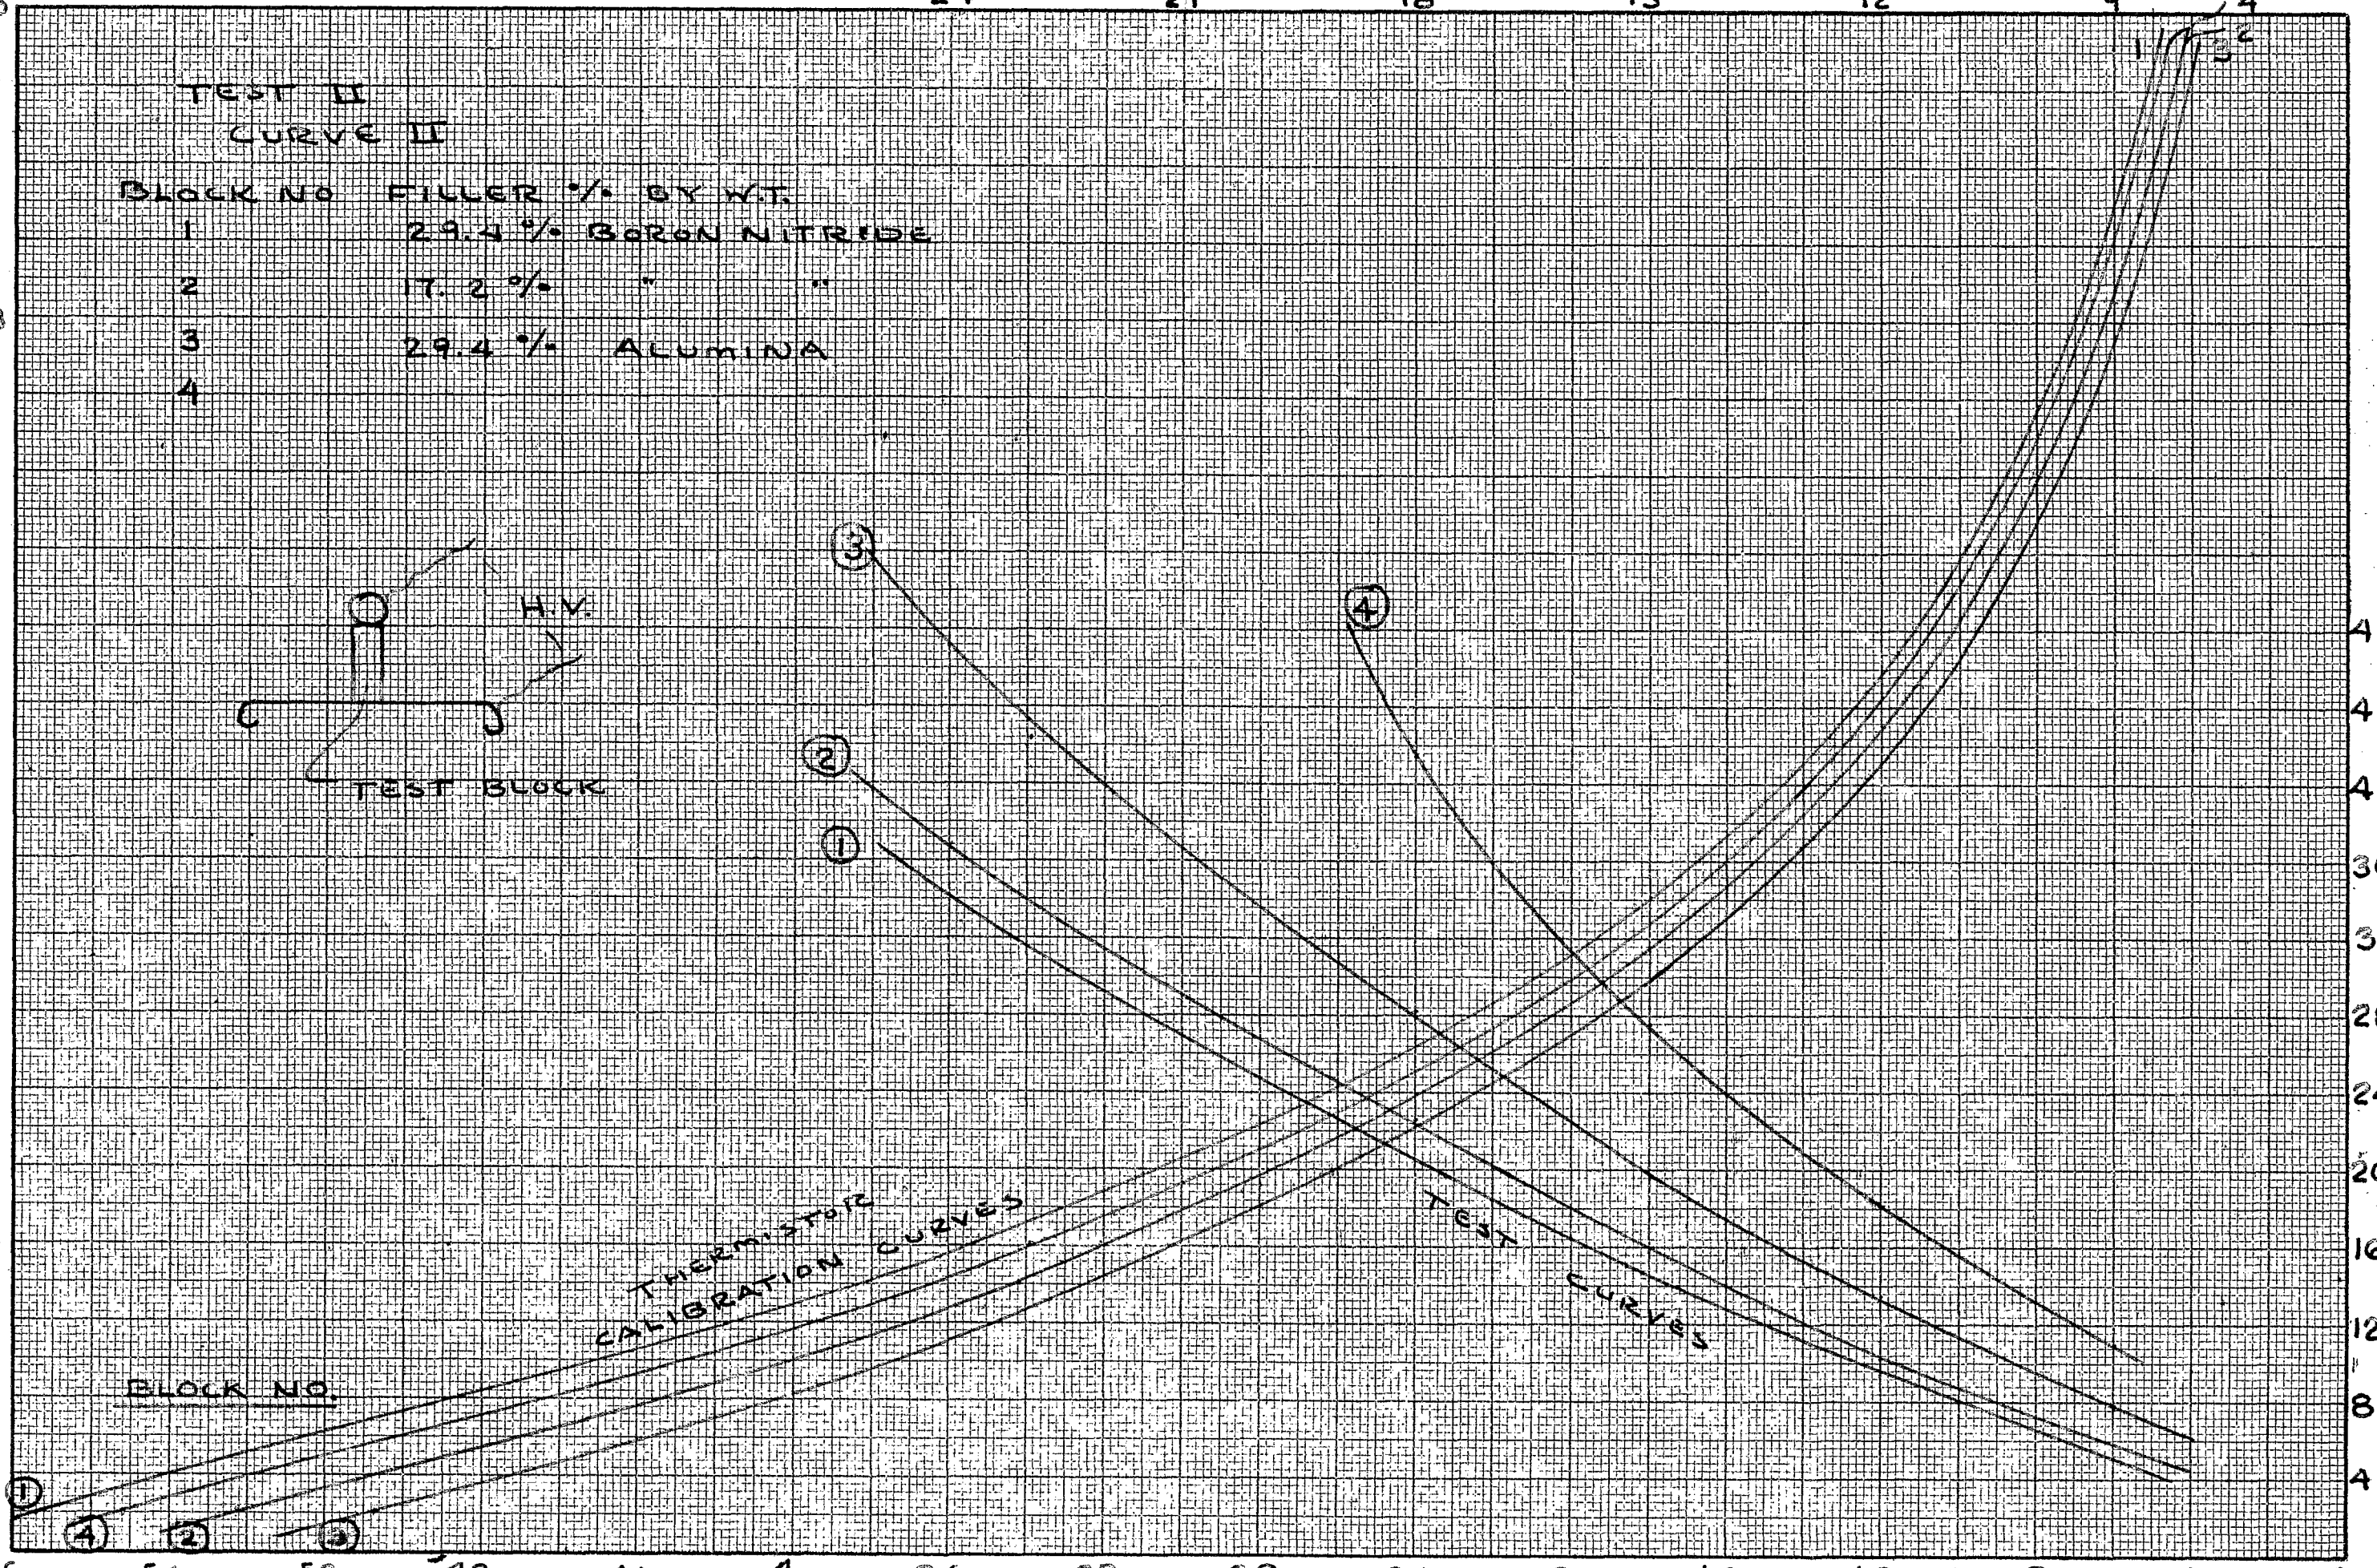

Block Failure AT

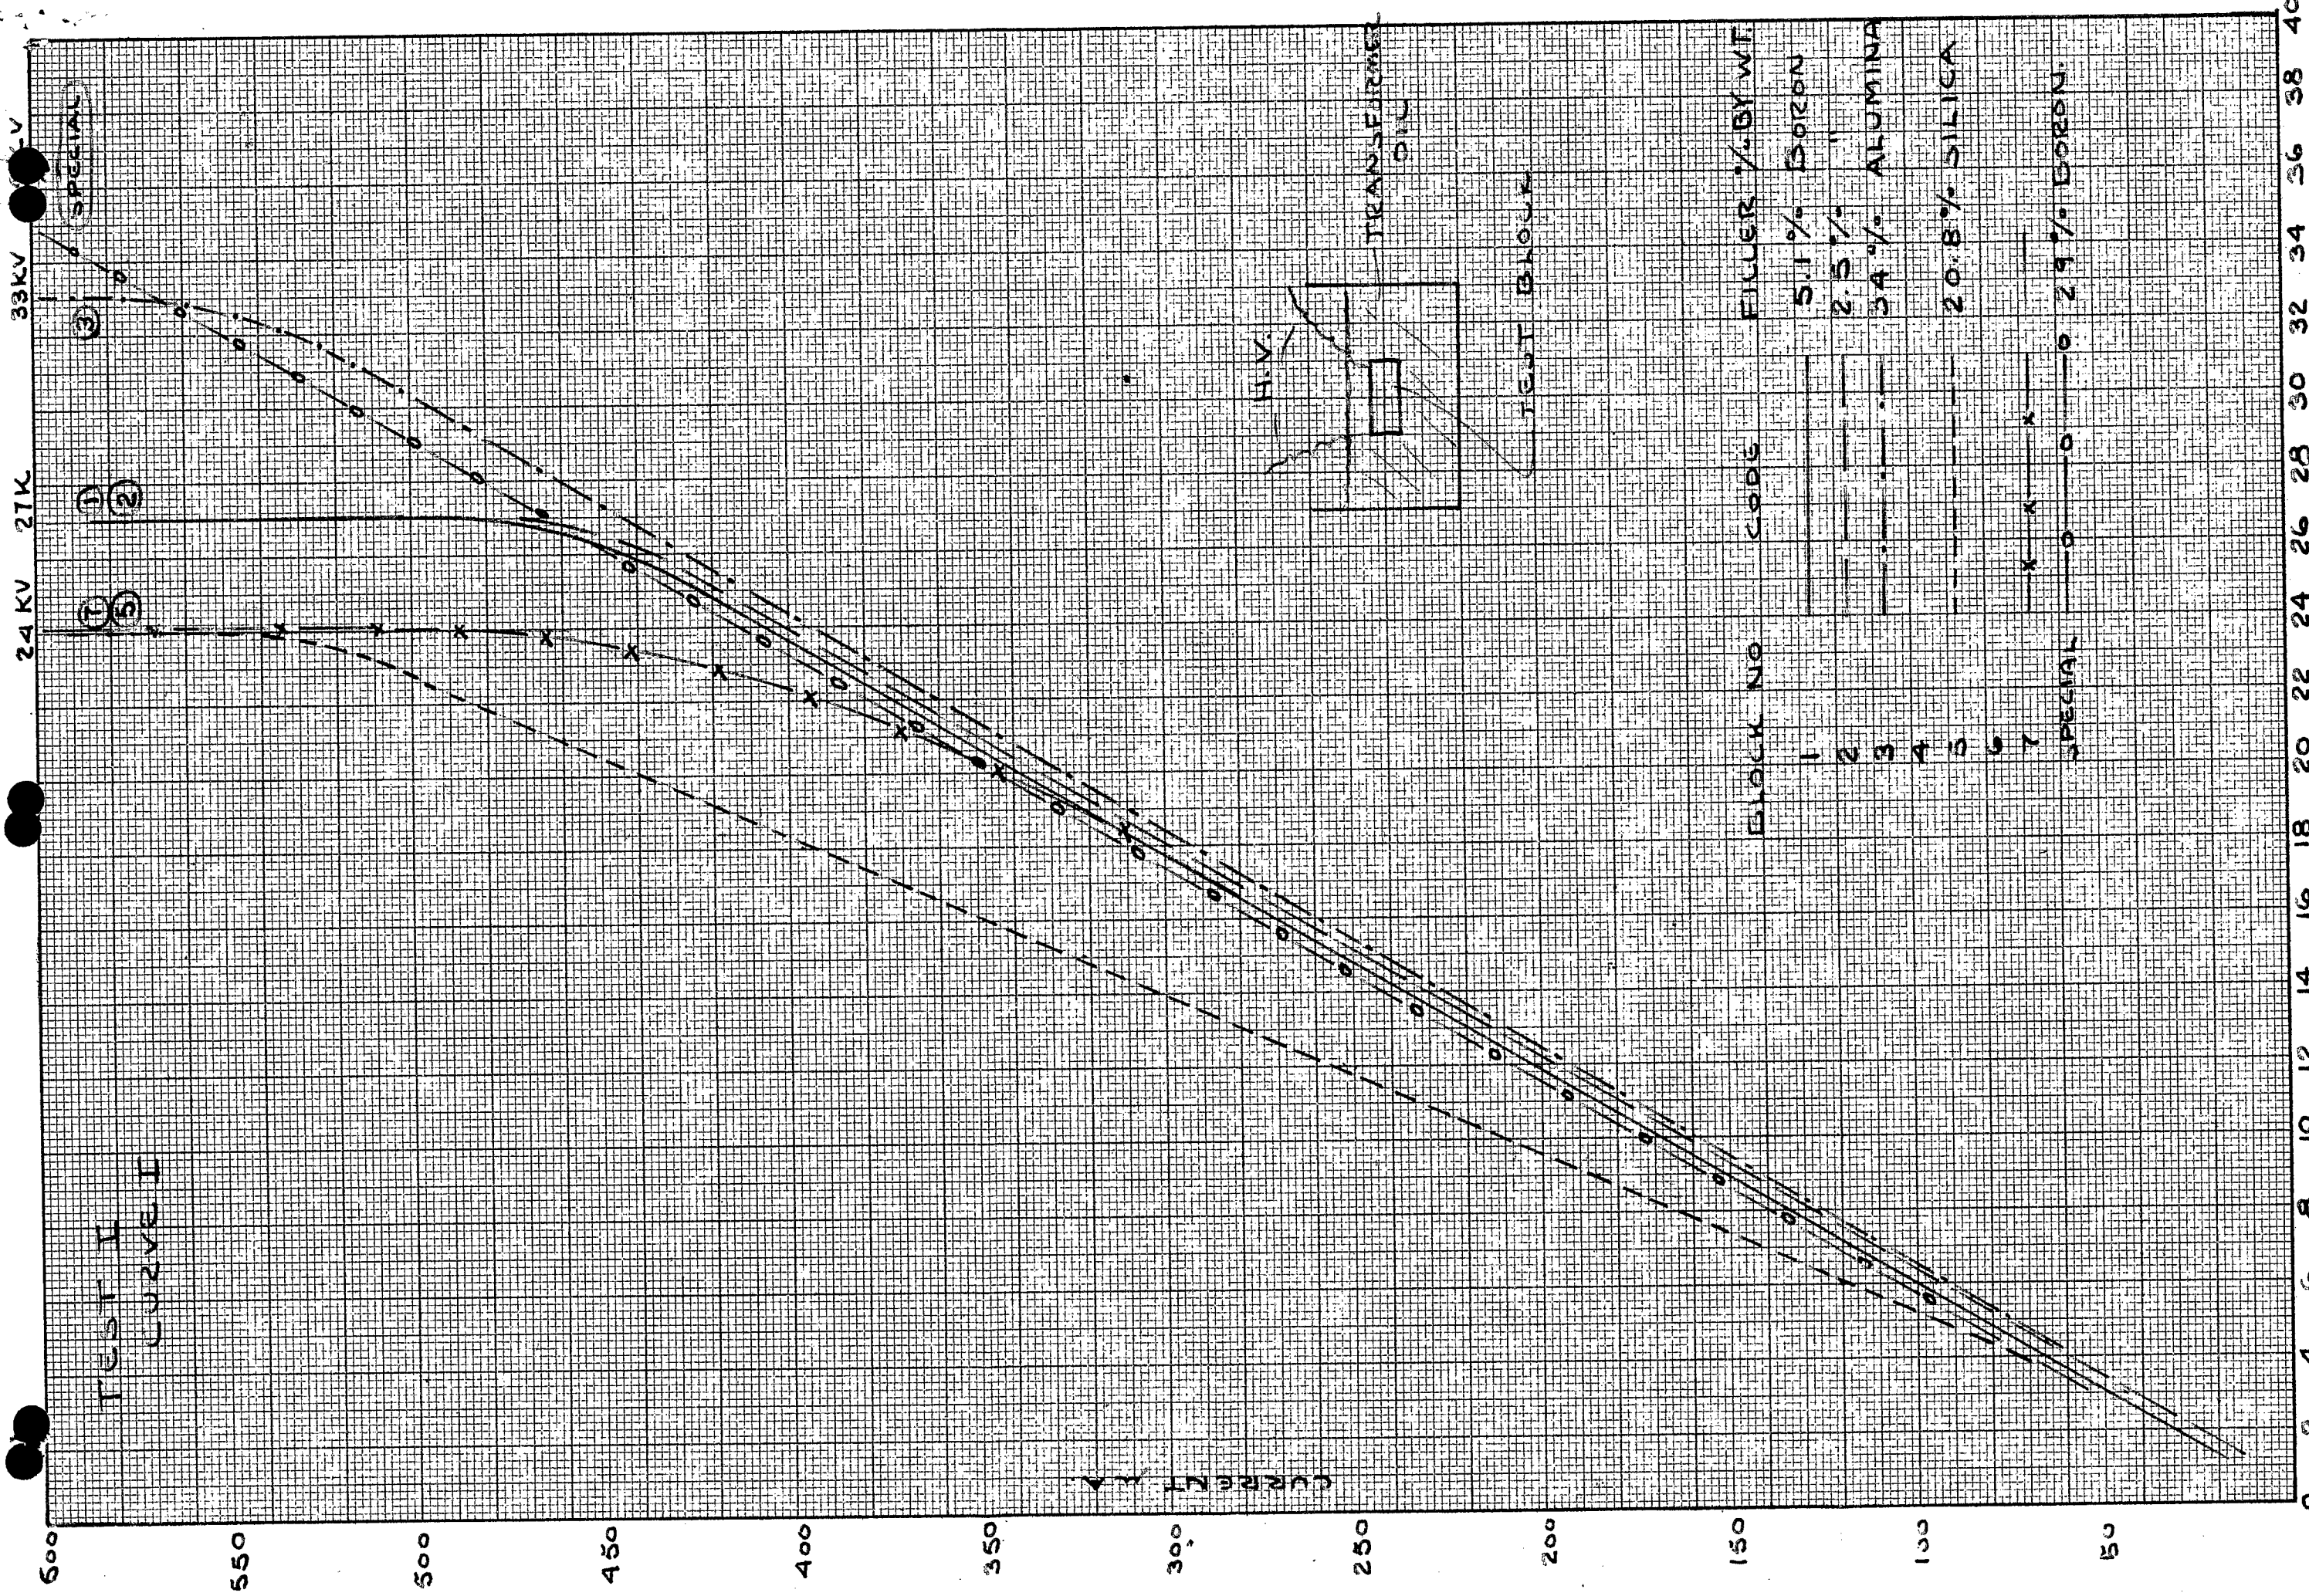

TEST I
CURVE I

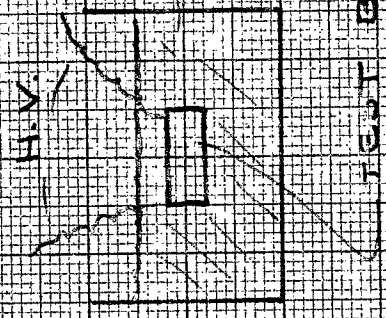

Block No	CODE	FILLER % BY WT
1	---	5.1% BORON
2	---	2.5% "
3	---	34% ALUMINA
4	---	20.8% SILICA
5	---	---
6	---	---
7	X X X	---
SPECIAL	---	2.9% BORON