

IMPROVED MECHANICAL SEAL FOR ALUMINUM VACUUM WINDOWS

E. S. Rodger

December 1982

Collider Accelerator Department
Brookhaven National Laboratory

U.S. Department of Energy

USDOE Office of Science (SC)

Notice: This technical note has been authored by employees of Brookhaven Science Associates, LLC under Contract No.DE-AC02-76CH00016 with the U.S. Department of Energy. The publisher by accepting the technical note for publication acknowledges that the United States Government retains a non-exclusive, paid-up, irrevocable, world-wide license to publish or reproduce the published form of this technical note, or allow others to do so, for United States Government purposes.

DISCLAIMER

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, nor any of their contractors, subcontractors, or their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or any third party's use or the results of such use of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof or its contractors or subcontractors. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

Accelerator Department
BROOKHAVEN NATIONAL LABORATORY
Associated Universities, Inc.
Upton, New York 11973

AGS Division Technical Note
No. 184

IMPROVED MECHANICAL SEAL FOR ALUMINUM VACUUM WINDOWS

E. Rodger

December 13, 1982

Summary

This Technical Note analyzes past problems associated with the vacuum windows on our secondary emission chambers, describes a new seal and its testing and performance to date.

Introduction

The proper operation of a secondary emission chamber generally requires vacuum levels of $10^{-9}/10^{-8}$ Torr. This in turn requires a bake-out at 300°C . The high vacuum and bake requirement placed stringent sealing demands on the particle windows of the unit. In the past, these windows were made of 0.002" thick stainless steel which was E.B. welded around its circumference. Once welded, they were generally leak tight. There were two problems, however; first, a high rate of rejects during the welding operation and second, the relatively high atomic number of stainless steel was in some cases objectionable. An aluminum window of 0.003" thick, 5052H35 was then tried making use of a mechanical seal as shown below.

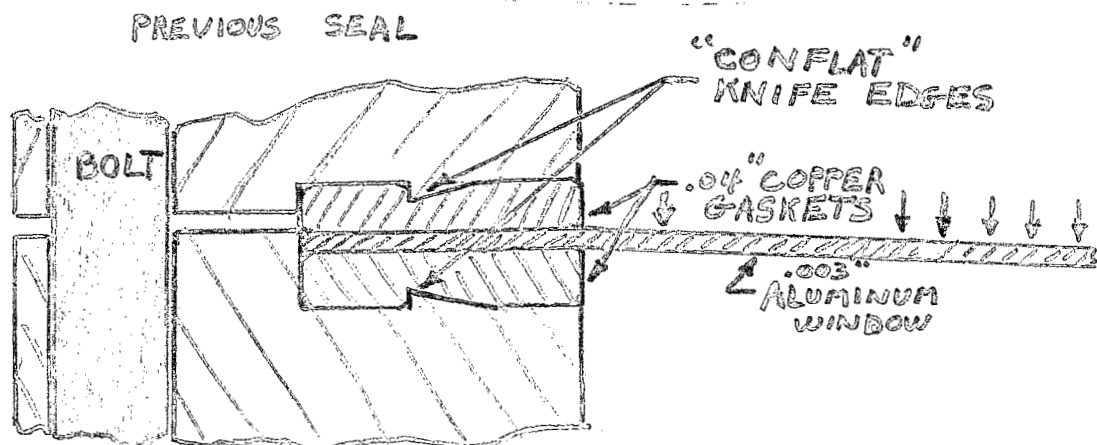


FIG. 1

This design proved troublesome for two reasons. First, the copper-to-aluminum seal was marginal because the high stress of the knife edge-to-copper contact was dissipated in traveling through the copper. This was evident by the fact that the minute surface scratches on the copper gasket were not completely obliterated by the window at the sealing area. Second, extensive copper-aluminum corrosion was observed across the seal area on a leaking unit. These observations lead to the design of a mechanical seal in which the stainless flange is clamped directly to the aluminum window as shown below.

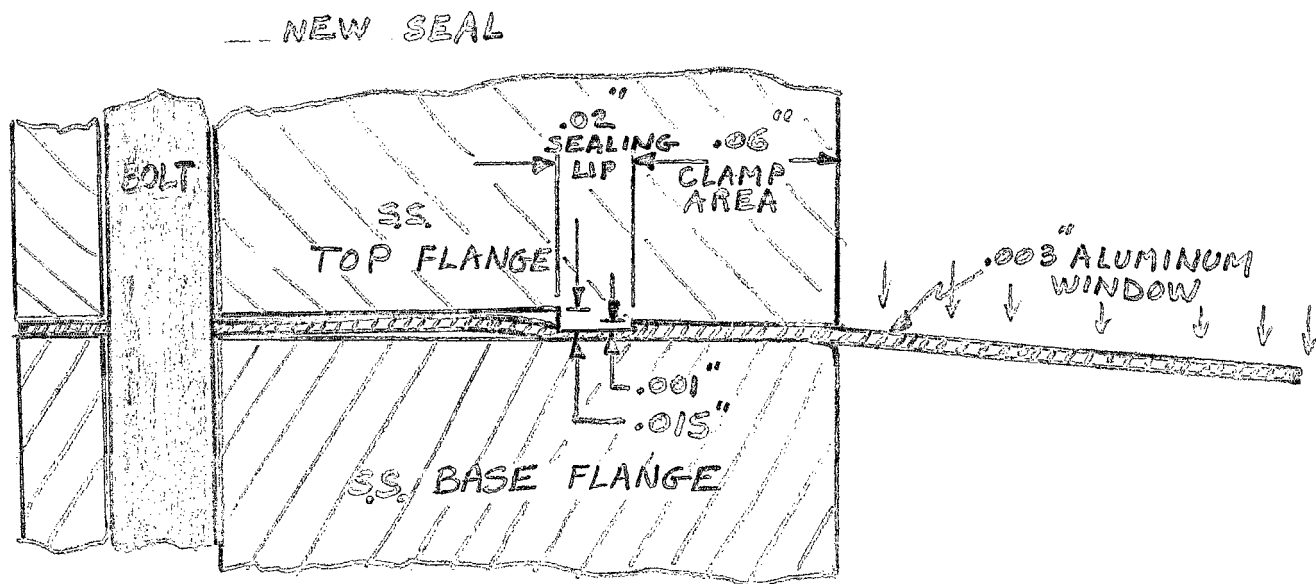


FIG. 2

This seal has three significant features:

1. Elasticity is built into the flange by the 0.015" relief in the bolt area. This causes the flange to take a slight cone shape under bolt tension. This maintains force on the sealing lip over temperature extremes and differential expansions.
2. The sealing lip is raised 0.001" + 0.0005" above the clamping area and is 0.02" wide. The contact area of the lip with the aluminum is such that under 200 in-lbs. of bolt torque, the compressive yield of the aluminum window is exceeded by a factor of about three. The lip thus sinks into the aluminum until the clamping area comes in contact.

3. The clamping area is compressed against the window with a stress which is approximately equal to the yield of the aluminum. This assures a good mechanical grip to resist the vacuum force.

Photographs taken at 38x of the seal areas of the flange and window are included. The machining marks on the stainless flange are readily observed embossed into the aluminum as well as the 0.001" depression left by the sealing lip (cross section photo). Also, note the microscopic grain and surface irregularities of the window material are obliterated in the seal and clamping areas.

Testing to date consists of five seals made with the same flange set. None showed any leak on the most sensitive scale of a helium mass spectrometer as shown below.

<u>Test #</u>	<u>Condition</u>	<u>Results</u>
1	As assembled (room temp.)	no leak
2	Assembled then baked @ 250°C	" "
3	Assembled, baked 2 hrs. at 250°C, cooled slowly to 100°C, sprayed with cold water	" "
4	Assembled, baked 2 hrs. at 300°C, cooled slowly to 200°C, sprayed with cold water	" "
5	Assembled, baked 2 hrs. at 300°C, sprayed with cold water	" "


An S.E.C. has been assembled using the new seal and is presently installed in the U Line for operational testing.

mn

Distribution: Dept. Admin.
 E. Jablonski
 Y.Y. Lee
 A. Soukas
 J. Tuozzolo
 W. Van Zwienen
 P. Yamin

WINDOW UPPER SIDE

(38X)

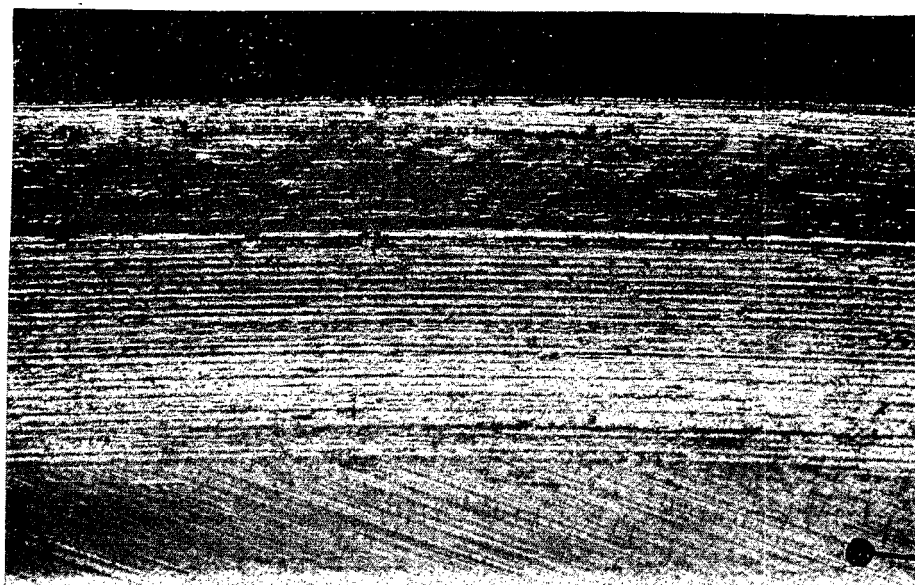

SEAL AREA


CLAMP AREA

UNDISTURBED GRAIN

FIG. 3

TOP FLANGE
(MATES WITH FIG. 3)

(38X)

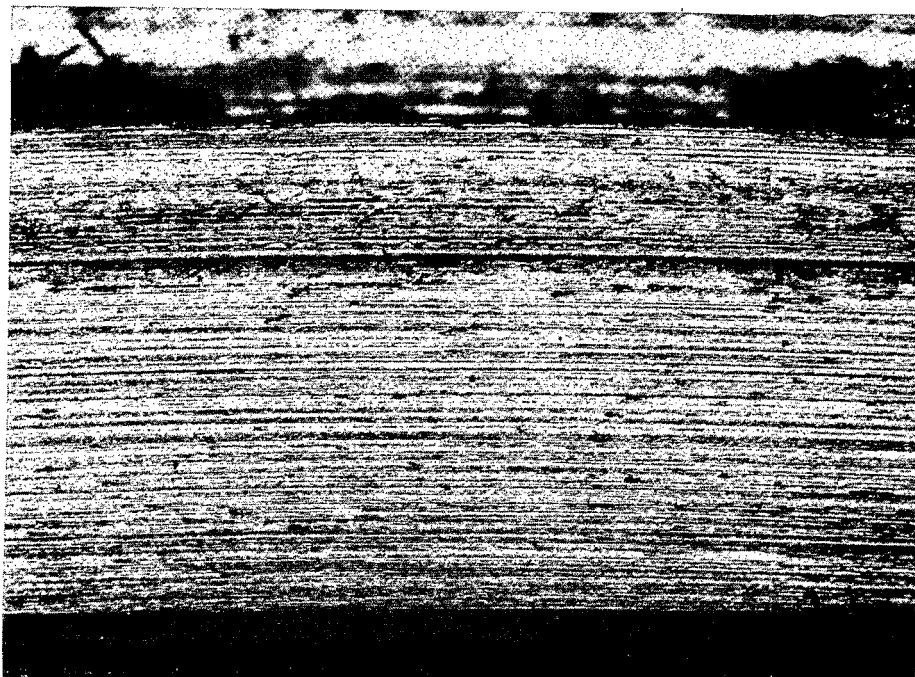


SEAL AREA

CLAMP AREA

FIG. 4

WINDOW LOWER SIDE

(38X)

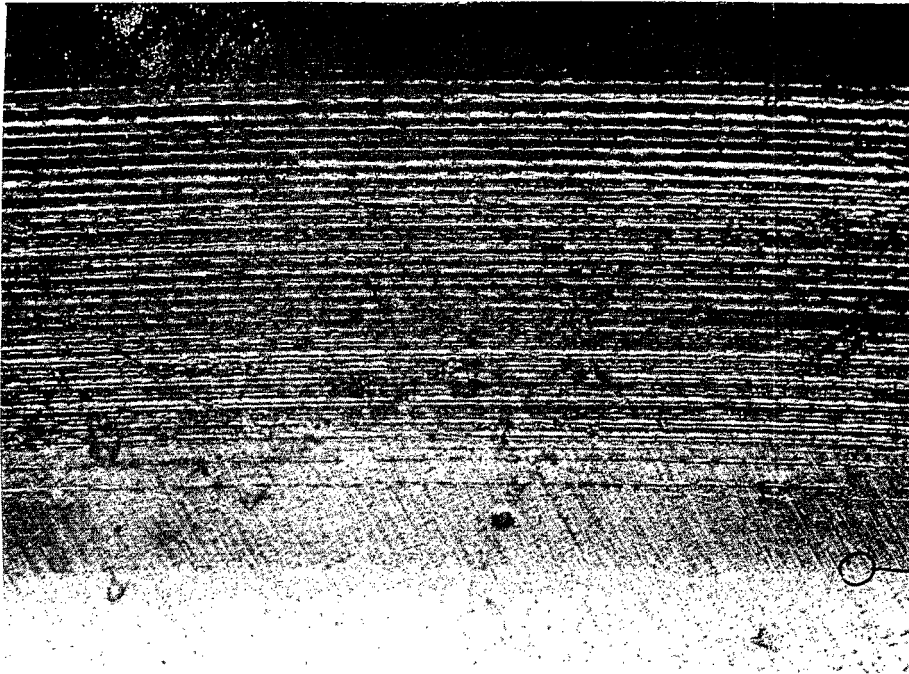

UNDISTURBED
GRAIN

FIG. 5

BASE FLANGE
(MATES WITH FIG. 5)

(38X)

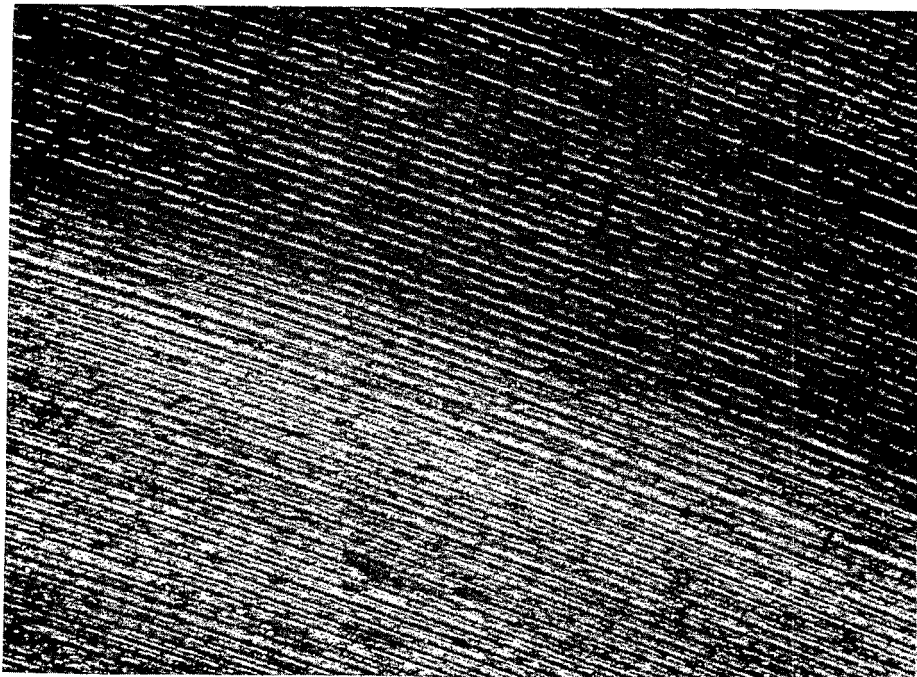


FIG. 6

CROSS SECTION OF WINDOW
SEAL/CLAMP AREAS

(38X)

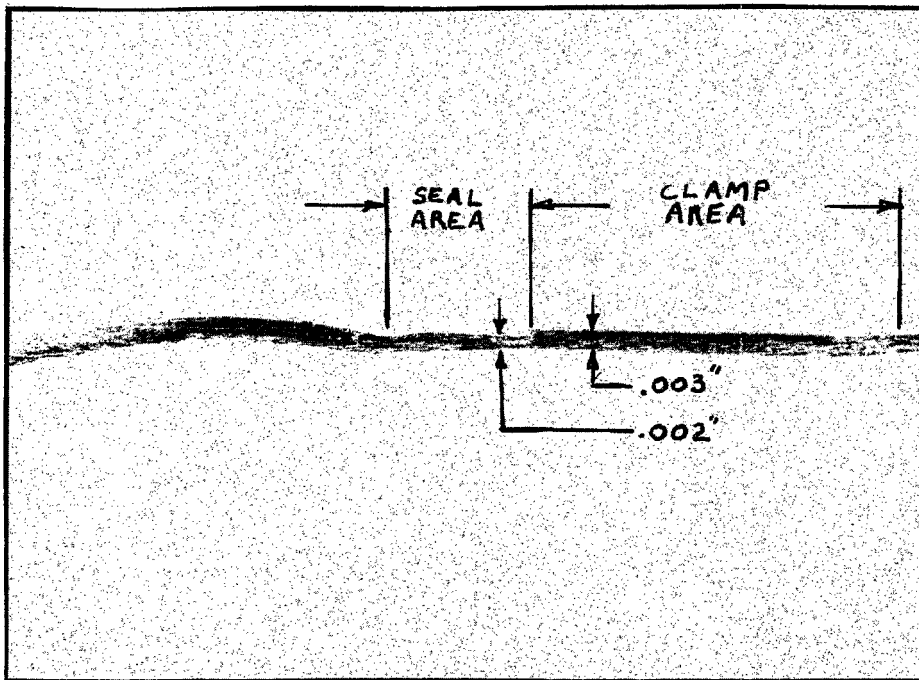


FIG. 7